



Resonant Optical Antennas
P. Mühlischlegel, *et al.*
Science **308**, 1607 (2005);
DOI: 10.1126/science.11111886

***The following resources related to this article are available online at
www.sciencemag.org (this information is current as of October 29, 2007):***

Updated information and services, including high-resolution figures, can be found in the online version of this article at:

<http://www.sciencemag.org/cgi/content/full/308/5728/1607>

Supporting Online Material can be found at:

<http://www.sciencemag.org/cgi/content/full/308/5728/1607/DC1>

A list of selected additional articles on the Science Web sites **related to this article** can be found at:

<http://www.sciencemag.org/cgi/content/full/308/5728/1607#related-content>

This article **cites 29 articles**, 3 of which can be accessed for free:

<http://www.sciencemag.org/cgi/content/full/308/5728/1607#otherarticles>

This article has been **cited by** 84 article(s) on the ISI Web of Science.

This article appears in the following **subject collections**:

Physics, Applied

http://www.sciencemag.org/cgi/collection/app_physics

Information about obtaining **reprints** of this article or about obtaining **permission to reproduce this article** in whole or in part can be found at:

<http://www.sciencemag.org/about/permissions.dtl>

Resonant Optical Antennas

P. Mühlischlegel,¹ H.-J. Eisler,¹ O. J. F. Martin,² B. Hecht,^{1,*}
D. W. Pohl¹

We have fabricated nanometer-scale gold dipole antennas designed to be resonant at optical frequencies. On resonance, strong field enhancement in the antenna feed gap leads to white-light supercontinuum generation. The antenna length at resonance is considerably shorter than one-half the wavelength of the incident light. This is in contradiction to classical antenna theory but in qualitative accordance with computer simulations that take into account the finite metallic conductivity at optical frequencies. Because optical antennas link propagating radiation and confined/enhanced optical fields, they should find applications in optical characterization, manipulation of nanostructures, and optical information processing.

Efficient interconversion of propagating light and localized, enhanced fields is instrumental for advances in optical characterization (1–5), manipulation (6–8), and (quantum) optical information processing (9–13) on the nanometer scale. This requirement recently triggered a search for favorable structures (1–5, 13–21) and materials (10, 22). Resonant optical antennas excel among other structures by combining (i) field-line concentration at a local shape singularity, that is, a gap (2, 3); (ii) optimum impedance matching to freely propagating waves; and (iii) resonant collective oscillations (plasmons) of the free electron gas (4, 5, 11, 21) in the antenna arms. While the field enhancement in the feed gap obviously increases with decreasing width (20), variation of the overall antenna length should result in a pronounced resonance in analogy to the radio wavelength regime.

We demonstrate that gold dipole antennas can be designed and fabricated to match optical wavelengths. Upon illumination with picosecond laser pulses, white-light supercontinuum (WLSC) (23–25) radiation is generated in the antenna feed gap in addition to two-photon photoluminescence (TPPL) (20, 26, 27) in the antenna arms. The emission from the antennas is more than 10^3 times as strong as that from solid gold stripes of the same dimensions but without feed gap. Variation of the overall length of the antenna reveals a resonance substantially below one-half of the effective excitation wavelength.

The nanometer-scale dimensions of resonant optical antennas raise a twofold experimental challenge, that is, manufacturing with sufficient precision and identification of specific antenna effects. The first challenge can be met by means of modern microfabrication

techniques, demonstrated for bow-tie antennas at infrared and, more recently, at optical frequencies (15, 16, 19, 20). We fabricated slim dipole antennas with lengths in the half-wavelength range by means of focused-ion beam (FIB) milling. In an initial step, sets of stripes with full length $L = 190$ to 400 nm and width 45 nm were cut from 40-nm-thick, micrometer-sized rectangular gold patches arranged well separated from each other on an indium tin oxide (ITO)-coated (10-nm thickness) glass cover slide. For complete gold removal, the FIB had to cut slightly into the substrate, leaving a shallow depression (~ 20 nm) around the stripes. In the final step, one-half of the stripes were converted into optically resonant antennas (ORA) by cutting a narrow groove through the centers of the stripes, leaving an ~ 20 -nm-wide gap between the ORA arms (Fig. 1, A and B). “Resonant” here refers to the laser excitation rather than to WLSC emission, because the permittivity of the substrate and the finite thickness of the antennas reduce the effective wavelength at the interaction zone to values considerably off resonance.

Specific antenna effects were identified with picosecond laser pulses powerful enough to excite WLSC in addition to TPPL and by comparing explicitly the responses of ORAs and stripes. TPPL is a second-order process well documented for gold (20, 26, 27). WLSC is a fourth-order optical nonlinearity found in various dielectric materials such as glass (23, 25) and water (24) but not in gold (20, 26, 27). WLSC hence provides information on the field enhancement outside the ORA arms. The mechanisms underlying WLSC are not well known but seem to require a minimum pulse length in the picosecond range. Both mechanisms contribute to the “white-light continuum” (WLC) recorded in our experiment, the respective contributions being distinguished by their spectral features and power dependences.

The sample was mounted in an inverted optical microscope modified for confocal operation in reflection (fig. S2A). Laser pulses [center wavelength $\lambda_0 = 830$ nm, rep-

etition rate 80 MHz, pulse length 8 ps at the sample (figs. S2B and S4), maximum average power $150 \mu\text{W}$, which is more than a factor of 5 below damage threshold] were focused (1.3 NA, ∞) to a diffraction-limited spot on the sample. The polarization at the sample was linear and adjustable in direction. The pulses were spectrally cleaned with a line filter before entering the microscope and blocked with a notch filter in front of the detectors. WLC spectra and power dependences of individual structures were obtained at fixed sample positions. WLC emission maps were recorded by scanning the sample with a single-photon-counting avalanche diode (SPAD) detector in combination with an additional bandpass filter (450 to 750 nm) (Fig. 1, C and D). The coincidence of the emission spots with the positions of ORAs and stripes was confirmed with a precision of better than 100 nm by comparison with large-scale scanning electron microscope (SEM) images and optical images (fig. S1). Sizeable WLC emission was found only at the positions of ORAs, for ORAs of a certain length range, and for ORA orientation along the pump polarization (e.g., Figure 1C, antenna #12). The emitted light is polarized along the ORA main axis as well, independent of the excitation polarization, which indicates the importance of the ORA also for the process of WLC emission (fig. S3). For comparison, signals from stripes are barely detectable (Fig. 1C, antenna #16) and are frequently associated

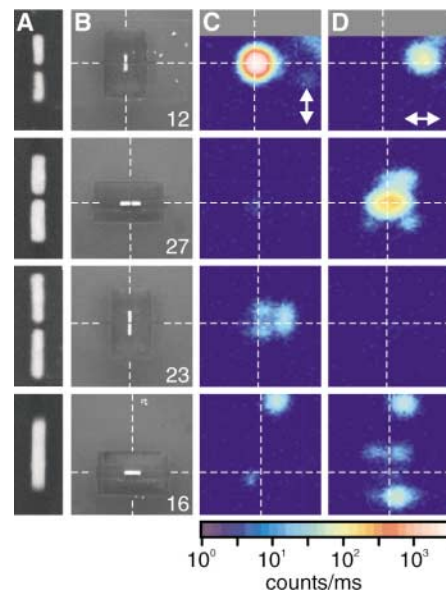


Fig. 1. Examples of ORAs and of a stripe. (A and B) SEM images, zoom and overview, respectively. (C and D) Confocal scan images of the WLC generated by vertically and horizontally polarized laser pulses, respectively (average power $110 \mu\text{W}$, logarithmic color code). Dimensions: (A) $450 \times 180 \text{ nm}^2$; [(B), (C), and (D)] $2 \times 2 \mu\text{m}^2$. An overview of all ORAs and stripes investigated (including enumeration) is presented in fig. S1.

¹Nano-Optics group, National Center of Competence in Nanoscale Science, Institute of Physics, University Basel, Klingelbergstrasse 82, CH-4056 Basel, Switzerland. ²Nanophotonics and Metrology Laboratory, Swiss Federal Institute of Technology Lausanne (EPFL), ELG 240, Station 11, CH-1015 Lausanne, Switzerland.

*To whom correspondence should be addressed. E-mail: bert.hecht@nano-optics.ch

with WLC generation at the rims of the depressions mentioned above.

The WLC spectra (Fig. 2) extend over a considerable range on both sides of the laser line, independent of antenna length. We concentrate here on the short-wavelength wing. At low power, the intensity falls off monotonously toward short wavelengths, typical for TPPL of gold (26, 27). At high power, the spectrum is dominated by a broad peak around 560 nm that we assign to WLSC. Figure 3 shows the dependence of WLC power on laser power for ORAs of different lengths. The log/log curves first rise with slope 2 (dashed lines), which is typical for TPPL. For high-power excitation, the curves follow a fourth-order power law (dashed-dotted lines), supporting the above assignment to WLSC. The nonlinearity of the WLC process was used to determine the laser pulse length right at the position of an ORA by means of the auto-correlation technique (fig. S4). Both Schuck *et al.* (20) and Beversluis *et al.* (27) report second-order behavior only, although the same materials and a similar range of excitation power are applied. The main differences from the present experiment are the use of femto- instead of picosecond laser pulses and of structures of a different, possibly less favorable, shape.


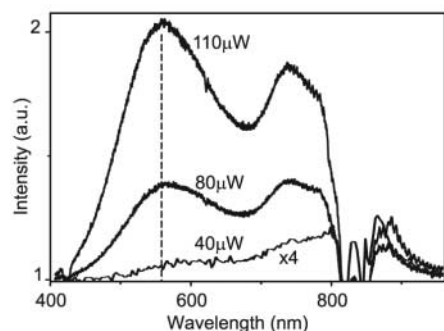


Fig. 2. WLC spectra of antenna #11 (fig. S1) for different excitation powers. Note the increase of the peak at 560 nm for increasing excitation power.

Fig. 4. (A) Variation of WLC power with antenna/stripe length. Filled and open squares, ORA at 110 and 30 μW , respectively; circles, stripe at 110 μW (fig. S5); solid red and black curves, $R^2(L)$ and $R^4(L)$ for ORAs, respectively; dashed line, $R^2(L)$ for stripes. (B to D) Near-field intensity ($|\text{electric field}|^2$) enhancement factor computed 10 nm above a stripe ($250 \times 40 \text{ nm}^2$), a resonant antenna ($250 \times 40 \text{ nm}^2$), and an off-resonant antenna ($410 \times 40 \text{ nm}^2$), feed gap 30 nm, gold on glass, $\lambda = 830 \text{ nm}$, $\epsilon = -25.3 + i1.6$ (30) and 2.25, respectively. Enhancement factor refers to $|\text{electric field}|^2$ of an evanescent field in the absence of the antenna. Scaling factor in (B) and (D), 10x. Scale bar, 200 nm.

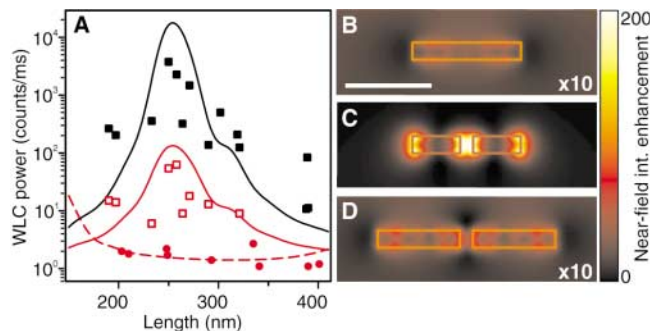

The variation of WLC power with ORA/stripe length (L) is displayed in Fig. 4A (see also fig. S5) for low- and high-power excitation corresponding to a dominance of TPPL and WLSC, respectively. For the shortest and longest lengths, the antenna emission is about 10 times as strong (30 μW) and 100 times as strong (110 μW), respectively, as the emission of the corresponding stripes. The antenna emission goes through a maximum in between, whereas the stripe emission hardly varies over the whole range of lengths. The ratio of emission intensities reaches values as large as ~ 30 (antenna #17, $L = 258 \text{ nm}$) and ~ 2000 (antenna #12, $L = 250 \text{ nm}$), respectively. The emission data scatter considerably between individual antennas, although Fig. 4A includes only structures that showed a high degree of perfection in the SEM (fig. S1B). This suggests that the WLC emission might be influenced also by material imperfections not visible in the SEM.

We computed the near-field intensity ($|\text{electric field}|^2$) enhancement 10 nm above ORAs and stripes versus length L in steps of 20 nm, using Green's tensor technique (28). Figure 4, B to D, reveals drastic differences between antennas and stripes of the same length as well as between antennas of different

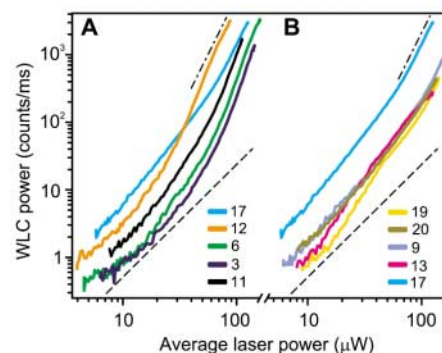


Fig. 3. WLC power dependence of ORAs with different lengths, grouped according to the dominant nonlinearity. (A) Fourth order, dashed-dotted line. (B) Second order, dashed line.

lengths. This refers to both spatial distribution and amplitude of the enhancement. The strong field concentration in the feed gap of the resonant antenna (Fig. 4C) suggests that WLSC is generated mainly in the underlying ITO/glass substrate, and possibly also in water that might condense inside the gap. Further increase of the enhancement may be expected from reduction of the feed gap width (20, 29).

As a figure of merit for the antenna response, $R(L)$, we use the near-field intensity, integrated, that is, averaged over the whole antenna area plus its immediate environment ($600 \times 200 \text{ nm}^2$). Although this is a somewhat arbitrary choice, the similarity of $R^2(L)$ and $R^4(L)$ with the experimental data is apparent, showing a flat response for the stripes but a pronounced peak for the ORAs for the same antenna length as in the experiment (Fig. 4A). No fit parameters were used in Fig. 4A except for a scaling factor.

We identify the $L_0 \sim 255\text{-nm}$ maximum, seen in experiment and simulation, with the so-called half-wave dipole resonance that might as well be considered a plasmon mode with strong field concentration in the feed gap (Fig. 4B). The latter effect is specific for the optical regime where the permittivity of gold is small (30). This prevents the design of ORAs by simple downscaling of radio-wave antennas. WLSC originating from the feed gap volume provides unusual illumination properties that may allow for new forms of local spectroscopy (for instance, single-molecule Raman) and interactions with nanostructures and single-quantum systems.

References and Notes

- K. Kneipp *et al.*, *Phys. Rev. Lett.* **78**, 1667 (1997).
- B. Knoll, F. Keilmann, *Nature* **399**, 134 (1999).
- A. Hartschuh, E. J. Sanchez, X. S. Xie, L. Novotny, *Phys. Rev. Lett.* **90**, 095503 (2003).
- J. B. Jackson, S. L. Westcott, L. R. Hirsch, J. L. West, N. J. Halas, *Appl. Phys. Lett.* **82**, 257 (2003).
- A. J. Haes, W. P. Hall, L. Chang, W. L. Klein, R. P. Van Duyne, *Nano Lett.* **4**, 1029 (2004).
- L. Novotny, R. X. Bian, X. S. Xie, *Phys. Rev. Lett.* **79**, 645 (1997).
- H. Xu, M. Käll, *Phys. Rev. Lett.* **89**, 246802 (2002).
- A. J. Hallock, P. L. Redmond, L. E. Brus, *Proc. Natl. Acad. Sci. U.S.A.* **102**, 1280 (2005).
- J. R. Krenn *et al.*, *Phys. Rev. Lett.* **82**, 2590 (1999).
- S. I. Bozhevolnyi, J. Erland, K. Leosson, P. M. W. Skovgaard, *Phys. Rev. Lett.* **86**, 3008 (2001).
- S. A. Maier *et al.*, *Nat. Mater.* **2**, 229 (2003).
- W. L. Barnes, A. Dereux, T. W. Ebbesen, *Nature* **424**, 824 (2003).
- P. Michler *et al.*, *Science* **290**, 2282 (2000).
- D. W. Pohl, in *Advances in Optical and Electron Microscopy*, T. Mulvey, C. J. R. Sheppard, Eds. (Academic Press, London, vol. 12, 1991), pp. 243–312.
- R. D. Grober, R. J. Schoellkopf, D. E. Prober, *Appl. Phys. Lett.* **70**, 1354 (1997).
- Ch. Fumeaux, J. Alda, G. D. Boreman, *Opt. Lett.* **24**, 1629 (1999).
- D. W. Pohl, in *Near-Field Optics: Principles and Applications*, M. Ohtsu, X. Zhu, Eds. (World Scientific, Singapore, 2000), pp. 22–23 (http://monet.physik.unibas.ch/info/members/contact_dp.html).
- K. B. Crozier, A. Sundaramurthy, G. S. Kino, C. F. Quate, *J. Appl. Phys.* **94**, 4632 (2003).
- D. P. Fromm, A. Sundaramurthy, P. J. Schuck, G. S. Kino, W. E. Moerner, *Nano Lett.* **4**, 957 (2004).

